



Thioplast® EPS Polysulfides

Liquid polysulfide polymers with
reactive epoxy-end groups

Technical product information

Nouryon

Thioplast® EPS Polysulfide Resins

Epoxy-terminated liquid polysulfides

Introduction

Nouryon Functional Chemicals GmbH in Greiz, Germany, is the leading manufacturer of liquid polysulfide polymers with the trade name Thioplast® G polysulfides.

Thioplast® EPS polysulfides are epoxy-terminated, low-viscosity liquid polysulfide polymers derived from the SH-terminated polysulfide polymer Thioplast® G polysulfide. Thioplast® EPS polysulfides are telechelic polymers with outstanding properties which combine the flexibility of conventional Thioplast® G liquid polysulfide polymers with the toughness of standard Bisphenol A/F-Epoxy based resins.

Thioplast® EPS polysulfides can be used in formulations together with other epoxy resins to increase flexibility, adhesion, aging and weathering and to improve chemical resistance.

Thioplast® EPS polysulfides have been specifically developed for use in high performance coatings, sealants and adhesives formulations for both interior and exterior use.

Nouryon offers two types of epoxy-functionalized liquid polysulfide polymers: aromatic and aliphatic Thioplast® EPS polysulfides that exhibit different physicochemical properties and behavior. Both types are particularly well suited for heavy-duty surface applications on metal and concrete.

The major advantage of Thioplast® EPS polysulfides compared to other polymer types is their remarkable flexibility and superior chemical resistance. Plus, formulators enjoy these

performance characteristics from polysulfide polymers without having to deal with any annoying thiol odor. Furthermore Thioplast® EPS polysulfides are cured with common epoxy amine hardeners. There is no need to use curing agents containing heavy metals.

Permeability to water vapor is lower than with pure aromatic epoxy resins. That makes Thioplast® EPS polysulfides particularly suited for coating applications on steel and concrete. Moreover, Thioplast® EPS polysulfides show unique self-repair and crack-bridging behavior. Aliphatic Thioplast® EPS polysulfides are also excellent reactive diluents which can act as a high potential flexibilizer in classical Bisphenol A/F Epoxy-formulations.

Properties

The combination of a primary polysulfide structure in the polymer backbone and epoxy termination leads to a unique class of polymers which can be employed either as a single component or in combination with commercial aromatic glycidyl ether resins and other epoxies.

Thioplast® EPS polysulfides exhibit a number of remarkable properties:

- rapid curing at ambient temperature
- good adhesion on many materials
- adjustable flexibility
- high impact resistance
- chemical resistance to a number of diluted acids, alkalis and organic solvents
- efficient self-healing characteristic

The combination of liquid polysulfide and epoxy resins yields telechelic polymers showing

superior properties. In addition to excellent chemical resistance and good adhesion these hybrids can be cured with a wide range of curing agents.

The following table displays which Thioplast® EPS type is best for which application


Table 1: Applicability of Thioplast® EPS grades.

Type	Coatings	Paints	Adhesives	Sealants
EPS35	+++	+	++	+++
EPS70	+++	++	++	+
EPS80*	+++	++	++	+

*US market only, because of TSCA-regulation

Chemical structure

The polymer's structure is dominated by the polysulfide backbone with SS- and formal groups and highly reactive epoxy-end groups.

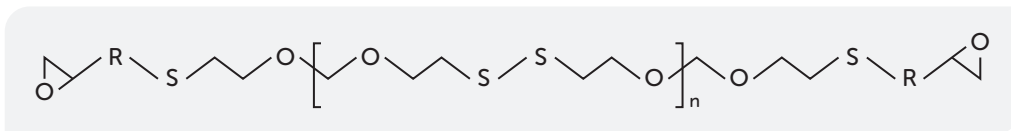

n<7

Curing of Thioplast® EPS polysulfides


As a rule, epoxidized polysulfides are formulated as two component systems and are cured at ambient temperature in the presence of a catalyst.

For example, component A could contain either a blend of Thioplast® EPS polysulfide with an epoxy resin, or solely Thioplast® EPS polysulfides, while component B could contain a compound with active hydrogen and a catalyst.

Preferred catalysts for curing Thioplast® EPS polysulfides are amines:

- aliphatic amines
- cycloaliphatic amines
- amidoamines
- aromatic amines
- polyamides

Curing occurs via the mechanism of a stoichiometric polyaddition reaction following the opening of the oxirane ring.

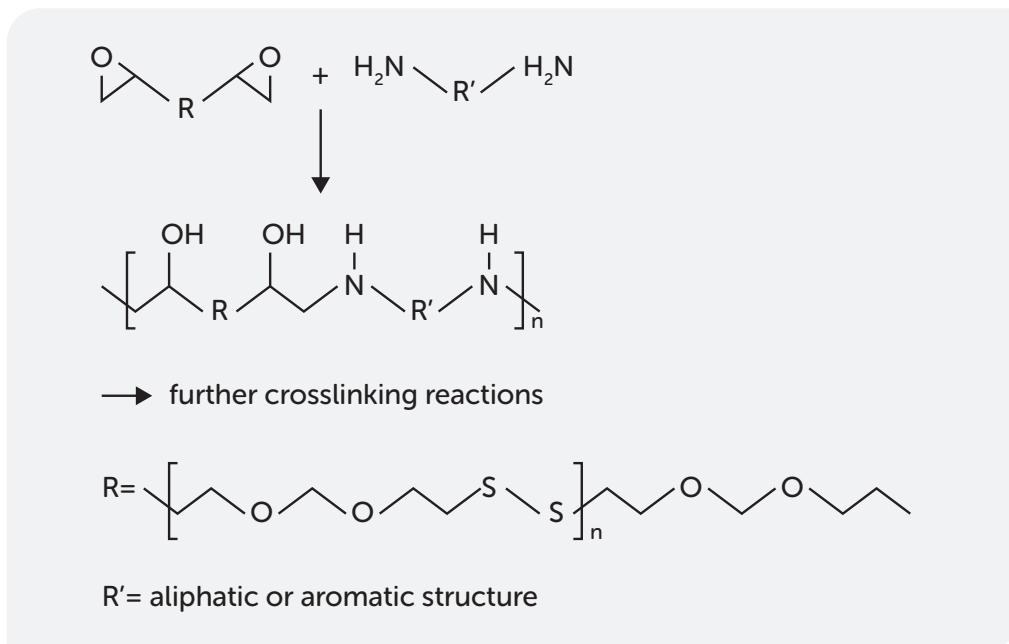

Compounds with active hydrogen are:

- polysulfides, polythiols
- primary or secondary amines (no additional catalysts necessary)
- polyols

Different Thioplast® EPS types

The possibility to use the whole range of Thioplast® G liquid polysulfides as a polymer backbone allows a great variability in viscosity and degree of branching of the resulting Thioplast® EPS polysulfides.

Thioplast® EPS35 purely aliphatic epoxy polysulfide is based on Thioplast® G polysulfides.

Chemical reaction with aromatic glycidyl ether derivatives with Thioplast® G polysulfides leads to formation of Thioplast® EPS70, EPS80 types with higher viscosity.

Type / Characteristic	EPS35	EPS70	EPS80*
Viscosity @ 20°C (Pas)	3-4	5-10	5-10
Degree of branching (mol%)	2	0	0
Polymer structure	Aliphatic	Aromatic / Aliphatic	
Density (g/ml @ 20°C)	1.23	1.20	1.20
Oxygen content (weight-%)	2.3-2.6	4.6-5.6	4.6-5.6
Epoxy-equivalent weight (g/Eq)	600-800	280-350	280-350
Appearance	Clear amber		

* US market only, because of TSCA-regulation

The most important application areas for Thioplast® EPS polysulfides result from their four basic properties:

- Excellent adhesion properties, particularly on concrete, metal, etc.
- Low vapour transmission properties
- Flexibility and impact resistance
- Chemical resistance

Relevant fields of application of Thioplast® EPS polysulfides are:

- Flexible coatings for concrete, steel and wood
- Coating systems for surfaces exposed to fuels and aggressive chemicals
- Reactive diluents for epoxy resins used in paints and adhesives
- Thioplast® EPS polysulfides may also act as a versatile flexibilizer for solvent-free and solvent-containing coating systems resulting in high chemical resistance even in thin layers.
- Suited for facilities used to store and handle substances which present high risk for contaminating water. Thioplast® EPS polysulfides can be formulated to satisfy the German law for such facilities ('LAU-regulation')

The following table provides an outline of possible applications of the most popular Thioplast® EPS polysulfides. Needless to say that the applications of EPS are not restricted to those presented in this table.

Table 2: Exemplary application areas for EPS products.

Application	EPS35	EPS70	EPS80*	
Buildings Civil Engineering Adhesives	Anti-Corrosive Coating or Lining for Concrete	•	•	•
	Elastic, Chemical Resistant Flooring	•	•	•
	Adhesives for Building Panels	•		
	Adhesives for Metals	•		
	Adhesives for Automobile Parts	•	•	•
Coating Lining	Anti-Corrosive Coating for Metals	•	•	•
	Chemical Resistant Coating	•		
	Impact Resistant Coating	•	•	•
Electrical	Potting, Casting	•		
	Electrical Insulator	•		
	Electrical Components	•		

* US market only, because of TSCA-regulation

General Thioplast® EPS polysulfide properties

Thioplast® EPS polysulfides is a versatile flexibilizer in solvent free coatings and shows superb chemical resistance even when applied in thin layers. Thioplast® EPS polymers add flexibility to epoxy resins and at the same time it improves the chemical resistance of the resulting coating or adhesive. Depending on the choice of the co-reactant, specific properties of the cured product can be fine-tuned (see **tables 3a and 3b**).

Table 3a: Co-reactant or hardeners of Thioplast® EPS polysulfides and their effect on coating performance and characteristics. Features (Co-reactants and hardeners rated top to bottom from best to least suited)

Film		Chemical Resistance		
Flexibility	Adhesion	Acids	Solvents	Water
Best	Best	Best	Best	Best
Polyamide	Polyamide	Aromatic amine	Aliphatic amine	Polyamide
Amidoamine	Phenalkamine	Cycloaliphatic amine	Aliphatic amine adducts	Phenalkamine
Phenalkamine	Amidoamine	Aliphatic amine	Cycloaliphatic amine	Amidoamine
Cycloaliphatic amine	Cycloaliphatic amine	Aliphatic amine adducts	Aromatic amine	Cycloaliphatic amine
Aromatic amine	Aliphatic amine	Amidoamine	Polyamide	Aromatic amine
Aliphatic amine adducts	Aliphatic amine adducts	Phenalkamine	Phenalkamine	Aliphatic amine
Aliphatic amine	Aromatic amine	Polyamide	Amidoamine	Aliphatic amine adducts

Table 3b: Co-reactant or hardeners of Thioplast® EPS polysulfides and their effect on coating performance and characteristics. Features (Co-reactants and hardeners rated top to bottom from best to least suited)

Blush Resistance	Color Stability	Low Temp. Application	Corrosion Resistance	Viscosity
Best	Best	Best	Best	Best
Polyamide	Polyamide	Phenalkamine	Polyamide	Cycloaliphatic amine
Phenalkamine	Amidoamine	Aliphatic amine	Amidoamine	Aliphatic amine
Amidoamine	Cycloaliphatic amine	Aliphatic amine adducts	Phenalkamine	Amidoamine
Cycloaliphatic amine	Aliphatic amine adducts	Cycloaliphatic amine	Cycloaliphatic amine	Aromatic amine
Aromatic amine	Aliphatic amine	Polyamide	Aliphatic amine adducts	Aliphatic amine adducts
Aliphatic amine adducts	Phenalkamine	Amidoamine	Aromatic amine	Phenalkamine
Aliphatic amine	Aromatic amine	Aromatic amine	Aliphatic amine	Polyamide

Standard characteristics of regular, non Thioplast® EPS polysulfides modified, epoxy-systems are listed in **table 4**.

Table 4: Standard Epoxy-coating comparison chart

	Amine Epoxies	Polyamide Epoxies	Amidoamine Epoxies	Epoxy Phenolics / Novolacs
Description	Form very hard, adherent films with excellent chemical and corrosion resistance. Amine cured epoxies are often used as protective coatings and linings in highly corrosive environments. Amine epoxies require care in handling since the amines can be moderately irritating to the skin, and may cause allergic reactions.	Polyamide epoxies generally offer the widest latitude in coating formulation. They are considered more resilient and flexible, and have better weathering resistance and a longer pot life than amine cured epoxies. Polyamide epoxies generally have less solvent and acid resistance than amine cured epoxies.	Amidoamine are reaction products of a polyamine and a fatty acid. Their properties generally fall between those of amines and polyamides. They have good water and corrosion resistance like amines and good toughness like polyamides. They have relatively low molecular weights and low viscosities making them very good surface wetters	These coatings allow a wide range formulating latitude. Novolac epoxy resins increase the chemical resistance and solvent resistance. Increasing the level of phenolic increases the chemical and solvent resistance, but the coating loses flexibility.
Advantages	<ul style="list-style-type: none"> • Excellent alkali and water resistance • Very good acid resistance • Excellent solvent resistance • Hard, abrasion resistant film • Excellent corrosion resistance • Excellent wetting of substrate 	<ul style="list-style-type: none"> • Very good alkali and water resistance • Good acid resistance • Longer pot life than amines • Easy to apply • Cures more quickly than amines • Good weathering characteristics • Good film flexibility • Excellent adhesion 	<ul style="list-style-type: none"> • Excellent surface wetting • Excellent adhesion • Excellent water resistance • Low viscosity • Longer pot life than amines • Good gloss retention 	<ul style="list-style-type: none"> • High heat resistance • Excellent chemical resistance • Excellent solvent resistance • Excellent corrosion resistance • Hard, abrasion resistant film • Disadvantages and Limitations
Disadvantages and Limitations	<ul style="list-style-type: none"> • Amines can be irritating/toxic • Relatively short recoat time • Relatively short pot life • Slower dry than normal polyamides • Chalks/may discolor 	<ul style="list-style-type: none"> • Amines can be irritating/toxic • Relatively short recoat time • Relatively short pot life • Slower dry than normal polyamides • Chalks/may discolor 	<ul style="list-style-type: none"> • Slow cure • Fair color retention • Temperature dependent 	<ul style="list-style-type: none"> • Slow cure • Fair color retention • Temperature dependent

Self-repair capability

Intramolecular exchange of the S-S-bonds, as represented in **figure 1**, leads to a continuous rearrangement of these chemical bonds. This is the explanation for the excellent self-repair capabilities observed for cured Thioplast® EPS polysulfides.

To measure that self-repair capability, tensile testing experiments were performed to quantify the recovery of strength. Representative stress - strain curves for the original material are plotted in **figure 2a**, showing that the elongation at break is approx. $65 \pm 5\%$.

When a sample breaks during the tensile test and the fractures are immediately put into as close as possible contact and heated at 60 °C, the mechanical properties are fully restored in just 1 hour (**figure 2b**).

As expected, longer healing times lead to better healing, but even when the contact time between the two broken sections is as short as 15 min, a repaired sample shows an elongation at break close to 40%. Surprisingly, for all healing times, the stress - strain curves superimpose

and show only different elongations at break, indicating that the healed samples have similar elastic properties as the original material.

This material can be healed efficiently multiple times, and the mechanical properties after the second and third healing process are, within experimental error, fully restored, i.e., elongation at break of $\sim 63 \pm 5\%$, and no systematic decrease for consecutive breaking—healing cycles (**figure 2c** - page 8).

Figure 3 (page 8) shows the influence of the disulfide concentration on the self-healing properties of Thioplast® EPS polysulfide / Bisphenol A/F blends using different ratios of epoxy resins, one free of disulfide groups (DER732) and another containing disulfide groups in its structure (Thioplast® EPS).

Figure 1 : Intramolecular exchange of the S-S-bonds in Thioplast® EPS polysulfides as reason for the excellent self-repair capabilities

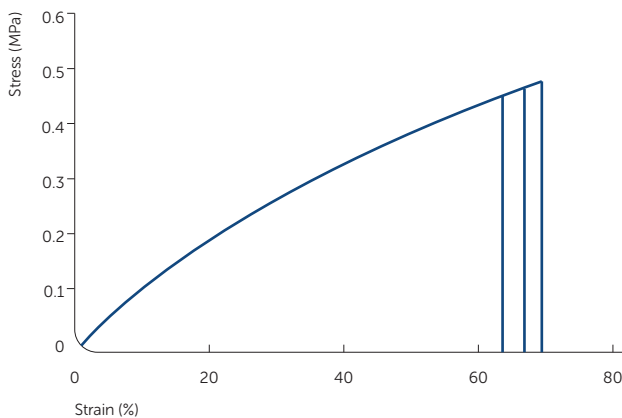
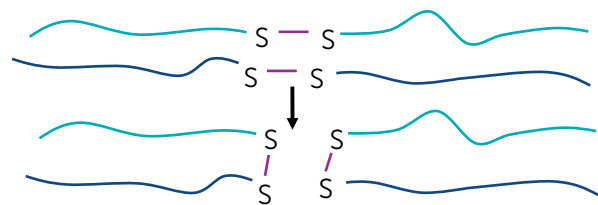


Figure 2a: Stress-strain curves of three different virgin samples to quantify the intramolecular exchange of the S-S- bonds in Thioplast® EPS polysulfides. Reference: Macromolecules 2011, 44, 2536-2541

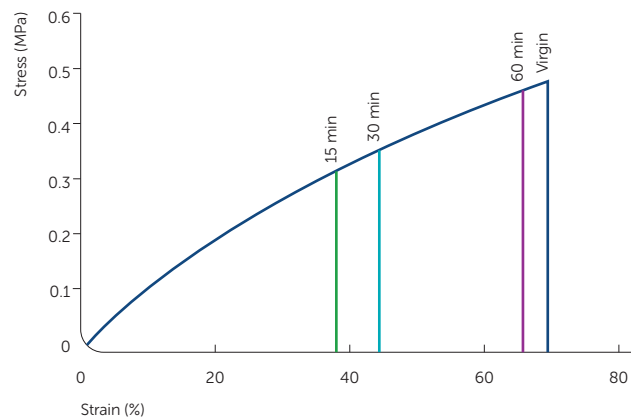


Figure 2b: Stress-strain curves of self-healed samples after different healing times.

■ Virgin ■ 15 min
■ 30 min ■ 60 min

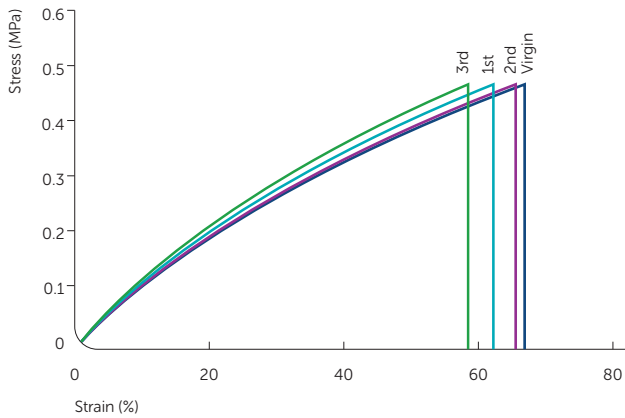


Figure 2c: Stress-strain curves of the virgin sample and of a self-healed sample after three breaking and healing cycles.

■ Virgin ■ 3rd
■ 1st ■ 2nd

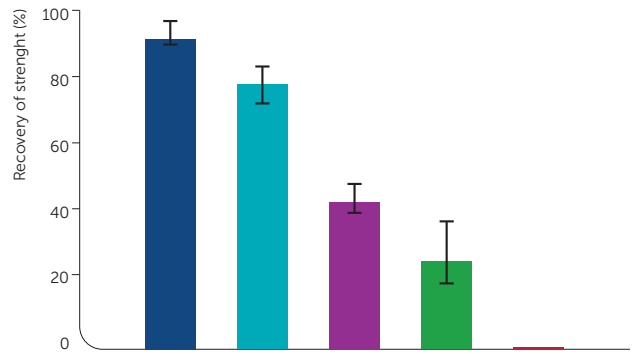


Figure 3: Recovery of strength (%) of healed samples with different concentrations of disulfide groups. Thioplast® EPS polysulfide / Bishenol A/F blends with different content of disulfide

■ Sample 1: 20 wt %; ■ Sample 2: 15 wt %;
■ Sample 3: 10 wt %; ■ Sample 4: 5 wt %;
■ Sample 5: 0 wt % disulfide.

Chemical resistance

Cured Thioplast® EPS polysulfides systems show outstanding resistance towards various chemical and corrosive attacks. They withstand a wide range of chemical substances: water, diluted acids, alkalis, esters, ketones, mineral oils and other hydrocarbons.

Table 5: Chemical resistance of Thioplast® EPS polysulfides

Substance	Resistance	Substance	Resistance
Acetone	+	Fuel oil	++
Formic acid conc.	-	Isopropanol	++
Formic acid 10%	+/D	Potassium hydroxide saturated solution	++
Ammonium hydroxide 32 %	++	Methanol	++
Gasoline	++	Sodium hydroxide saturated solution	++
Benzene	+	Phosphoric acid conc.	+/ D
Diesel 'Bio'-fuel	++	Nitric acid half conc.	++
Calciumhydroxide sat.sol.	++	Nitric acid conc.	-
Diesel fuel	++	Nitric acid 10%	+/ D
Diethyl ether	++	Hydrochloric acid conc.	+/ D
Dichloro methane	0	Hydrochloric acid 10%	+/ D
Acetic acid conc.	-	Sulfuric acid conc.	-
Acetic acid half conc.	+	Sulfuric acid half conc.	+/ D
Acetic acid 10%	++	De-icing salt	++
Ethanol	++	Toluene	++
Formaldehyde	++	Xylene	++

++ resistant for 14 d
 + resistant for 72 h
 0 resistant for 8 h
 - not resistant
 D discolouring

Specimens have been cured with a hardener based on a cyclo-aliphatic amine.

The resistance of Thioplast® EPS polysulfides to organic solvents and organic acids is better than that of epoxy resins.

Table 6: Chemical resistance of EPS compared to unmodified epoxy resin (EP)

	Days	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20	21	22	23	24	25	26	27	28																	
Acetone	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												
Toluene	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												
Methanol	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												
Diesel	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												
Benzene	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												
Acetic acid 10%	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												
Nitric acid 20%	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												
NaOH 50%	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												
NH ₃ 32%	EPS	no alterations observed																																												
	Epoxy	no alterations observed																																												

Viscosity and miscibility

Thioplast® EPS polysulfides are compatible with commercial epoxy resins. Viscosity can easily be adjusted by altering the ratio of the resin components in the mixture.

Odor

Due to the presence of mercaptan end groups unmodified polysulfide like Thioplast® G polysulfides have a characteristic odor. Since mercaptan end groups are absent in Thioplast® EPS polysulfides they lack this unpleasant odor.

Reactive behaviour

Epoxidized polysulfides can be cured using aliphatic, cycloaliphatic and aromatic amines, phenalkamine adducts and Mannich base type hardeners.

Adhesion


Adhesion of Thioplast® EPS polysulfides to concrete, glass and steel is better than of unmodified polysulfides.

Thermal shock resistance

Thioplast® EPS polysulfides tolerate thermal stress between - 55° C and 120 °C very well.

Aromatic Thioplast® EPS polysulfides

The chemical structure of the aromatic Thioplast® EPS grades is dominated by the polysulfide polymer chain and highly reactive epoxy end groups. The following scheme shows the chemical structure of aromatic EPS 70/80 resins. DGEBA/F is an abbreviation of Di-Glycidyl Ether of Bisphenol A/F resins.

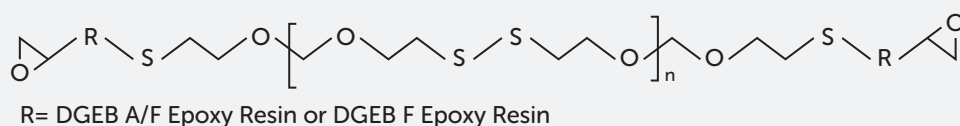

The addition of aromatic EPS 70/80 has only minimal effect on the reactivity of epoxy resins. The desired properties of the system can easily be adjusted by choosing the appropriate hardener system.

Tables 7a and 7b show examples of hardeners. Potting times were determined using EPS70 (or EPS80) and hardener at 23°C. With all hardeners, the resin was tack-free after 12-16 h. After seven days Shore D hardness was between 20 and 25. Adhesion on concrete was excellent and no difference between the various systems was noted. Concrete breakage occurred in all adhesion tests while the Thioplast® EPS polysulfides layer remained intact.

Table 7a: Examples of Hardeners to cure EPS70 / EPS80

Item	Chemical characteristics of Amine	H-Equivalent [g/Eq]	Potting time
Polylox H 445	Modified cycloaliphatic Polyamine	105	45 min
Polylox H 354	Mod. cycloaliphatic Polyamine	93	35 min
Polylox H 015	Mannich base, phenol free	75	20 min
Aradur 2964	Aliphatic and cycloaliph. polyamine	92	40 min
Aradur 450 S	Mod. polyamidoamine	115	45 min
Epilox 10 - 30	Mod. cycloaliphatic amino adduct	93	35 min
Epilox 10 - 32	Mod. cycloaliphatic polyamine	85	60 min
Epilox 10 - 38	Activated polyamine	95	30 min
Epilox 10 - 69	Amino adduct	46	30 min
Cardolite NC 566X80	Phenalkamin adduct	135	50 min

Table 7b: Examples of Hardeners to cure EPS70 / EPS80

Hardener	Chemical type of hardener	Curing @ 60°C (min)	Curing @ 23°C/ 50% rH (min)	ShoreA 7d@23°C/ 50% rH 5s value	ShoreA 14d@23°C/ 50% rH 5s value	Tensile strength (N/mm ²)	Elongation @ break (%)	Water absorption @ 23 °C After 14d (%)
Epikure 3223	Aliphatic Amine	20	100	96	92	16.58	38	2.23
Aradur 2973 CH	Aliphatic Polyamine	60, gelled	110, gelled	59.5	75	8.26	38	1.69
Aradur 2992 CH	Aliphatic Polyamine	10, gelled	20	50.9	78	9.66	83	2.34
Epikure 3601	Anhydride	150	240, gelled	59.9	95	34.19	3	1.27
Aradur 850 CH	Aromatic Amine Adduct	60, gelled	180, gelled	56.1	92	14.78	46	1.28
Aradur 863 XW 80 CA	Aromatic Amine Adduct	240, gelled	240, gelled	39.5	95	20.08	21	1.49
Polypox 060H	Cycloaliphatic Polyamine	60, gelled	90, gelled	60.9	88	10.59	48	1.67
Epikure 3370	Cycloaliphatic Polyamine	25	180	78	73	6.33	89	3.03
Epikure 3383	Cycloaliphatic Polyamine	50	240	70	70	6.49	63	1.83
Epikure 3115	Polyamides	50	240, gelled	92	91	11.17	41	2.8
Epikure 3140	Polyamides	35	240, gelled	91.5	89	15.73	48	2.37
Aradur 891 BD	Polyamidoamine	60 gelled	180, gelled	51.3	93	9.94	54	2.43
Epikure 3015	Polyamidoamine	35	240, gelled	72.5	75	3.88	62	2.74
Epikure 3046	Polyamidoamine	50	240, gelled	83.5	88	7.62	57	2.4
Aradur 460 J 90 BD	Polyamidoamine/ Ethanol	60, gelled	180, gelled	50.9	92	6.12	34	2.49
Aradur 465	Polyamine Adduct	40, gelled	50, gelled	53.1	72	6.51	68	1.3
Jeffamine D 230	Polyetheramines	90, gelled	24h, gelled	46.5	48	3.27	78	2.69
Jeffamine D 400	Polyetheramines	240, gelled	24h, gelled	39.9	53	1.15	36	3.08

The properties reported in **table 8** refer to mixtures of EPS70 and a Bisphenol A/F-resin Epilox T 19-27. A cycloaliphatic hardener, Aradur 2964, was used for curing.

Table 8: Properties of EPS70 / EPS blends and a Bisphenol A/F-resin (Hardener: Aradur 2964)

Epilox 19-27 (wt %)	0	20	40	60	80	100
EPS70 / EPS80 (wt %)	100	80	60	40	20	0
Viscosity (Pa*s)	8.7	8.2	7.8	7.5	7.3	7.2
Mixing ratio Resin : hardener	100:29.7	100:33.9	100:38.2	100:42.5	100:46.7	100:51
Potting time (min)	40	40	40	37	35	30
Shore D	22	35	55	63	70	75
Max. elongation after 28 d (%)	100	65	40	6	2	None

Weathering stability

Cured resin systems show very good resistance to weathering. Weathering resistance was determined by irradiating with Xenon arc light over a period of 500 h. With increasing Thioplast® EPS polysulfides content, the degree of yellowing and surface degradation is reduced. Pure EPS70 / EPS80 gives the best results and pure Bisphenol A/F resin the worst. Shore D hardness is hardly affected.

Flexibility

Elasticity and flexibility of cured Thioplast® EPS polysulfides is more than six times higher than that of pure aromatic epoxies based on Bisphenol A/F resin (**figure 4**). Addition of Thioplast® EPS polysulfides to Bisphenol-A/F-resins increases impact resistance. Starting from very hard, non-flexible epoxies one can produce coatings with low or high flexibility by varying the proportions of Thioplast® EPS polysulfides.

Impact resistance

It is possible to formulate very flexible epoxy coatings with simultaneous high hardness by using 55% EPS70/80 polysulfide. Impact strength increases to levels several times higher than before. Chemicals and mechanical properties meet the highest demands.

Good heat stability

The thermal degradation behaviour of EPS70/80 polysulfide and their formulations is very similar to that of conventional epoxy resins (**figure 5**).

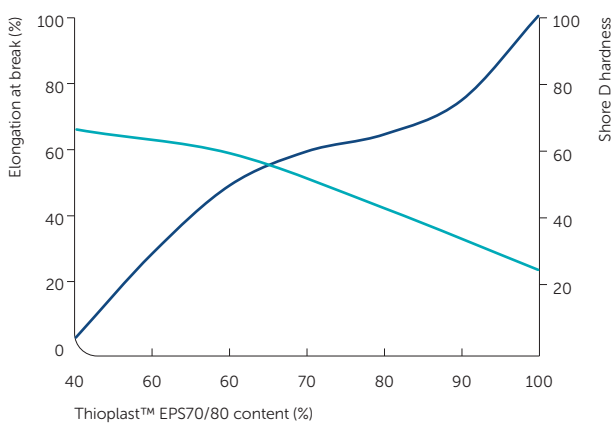


Figure 4: Increasing of elongation of cured Epoxy-resin by adding EPS70/80

— Shore D hardness
— Elongation at break (%)

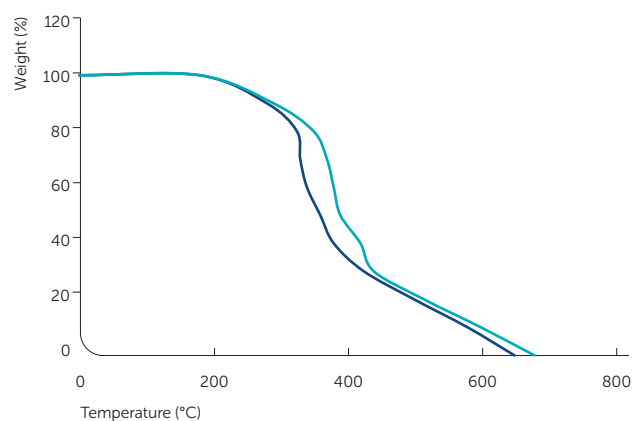


Figure 5: Thermogravimetric measurement of degradation of EPS70/80 and Bisphenol A/F resin

— A/F-resin
— EPS70

Aliphatic Thioplast® EPS

The aliphatic Thioplast® EPS35 polysulfides have been developed for exterior use. The low viscosity allows for the use as reactive and flexibilizing diluents for epoxy resins and for the aromatic epoxidized Thioplast® EPS70, EPS80 polysulfides. The chemical structure is dominated by the polysulfide polymer chain with aliphatic epoxy end groups.

Flexibility

The addition of EPS35 to regular Bisphenol A/F and Novolac resins results in highly flexible epoxies used in

- high-quality sealants and
- adhesives
- highly elastic, chemically resistant coating

Figure 7 shows the exceptional increase in flexibility of a standard Bisphenol A/F epoxy-based resin by the addition of EPS35. Even at concentrations as low as 10 %, an elongation of break of higher than 20 % is achievable with EPS35.

Formulations with high Thioplast® EPS content are easy to process. Mixtures consisting of aromatic and aliphatic Thioplast® EPS polysulfides result in extremely flexible, soft products.

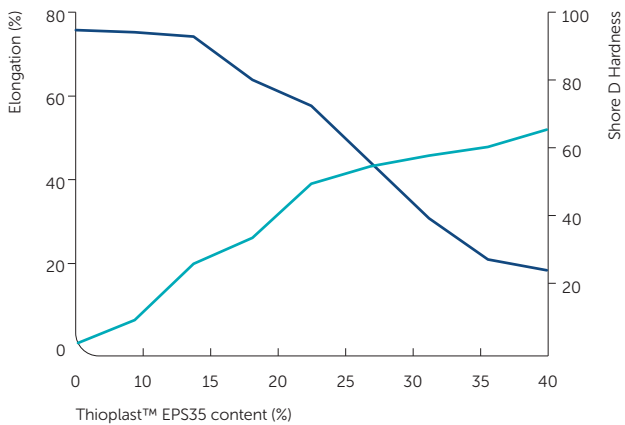


Figure 7: Variation of elongation and Shore D hardness with EPS35 content in standard formulations

— Elongation (%)
— Shore D hardness

Table 9 shows the unformulated stoichiometric curing of Thioplast® EPS35 polysulfide with some industry-standard amine curatives.

Table 9: Examples of hardeners to cure Thioplast® EPS35 polysulfide.

Hardener*	Chemical type of hardener	ShoreA 7d @ 23°C/50% rH 5s value	Tensile strength Elongation@break 1d 23°C/50% rH. + 14d 60 °C	
			[N/mm ²]	[%]
Epikure 3140	Polyamide	13.4	0.24	26.1
Aradur 891 BD	Polyamidoamine	32.9	0.39	34.6
Aradur 2973 CH	Aliphatic Polyamine	42.7	0.35	20.8
Aradur 450-1 S	Polyaminoamine	28.3	0.31	40.7
Aradur 15-1	Polyamine	6.6	0.10	60.0
Aradur 2965	Cycloaliphatic polyamine	38	0.41	34.8
Jeffamine D 400	Polyetheramines	13.2	0.2	60.9

* Thioplast® EPS35 polysulfides cured in a stoichiometric ratio



Starting formulations for Thioplast® EPS35 and EPS 70/80 polysulfides

Standard formulations using EPS70 / EPS80

Thioplast® EPS70 polysulfide works as a versatile flexibilizer for solvent-free coatings showing superb chemical resistance even when applied in thin layers. Thioplast® EPS polysulfides adds flexibility to epoxy resins and at the same time improves the chemical resistance of the resulting product.

Varying the ratio of Thioplast® EPS polysulfides to epoxy resin (by weight) allows for adjustment of properties according to specific needs of a particular application.

Table 10: Standard formulations for EPS70 or EPS80

	Formulation 1 green sample	Formulation 2 blue sample	Formulation 3 yellow sample
Component A			
Thioplast® EPS70 / 80 polysulfides	35	55	75
Bisphenol A/F resin*	40	20	-
Novarez LA 300**	5	5	5
Filler***	15	15	15
Pigment	5	5	5
Total component A	100	100	100
Component B			
Component B Aradur 2964	31	27	22
Potting time @23 °C (min)	30	32	35
Max. elongation (%)	4	10	70
Shore D @ 21d	60	39	22
Strength @ break (N/mm ²)	34	11.8	5.5

* A/F resin: Epoxy equivalent approx.180g/equiv.; Viscosity: 6000 - 8000 mPas. Also pure Bisphenol A-resins may be used.

** Instead of Novares LA 300 reactive diluents, benzyl-alcohol or other diluents suited for Epoxy resins may be used. When using such diluents check for adhesion decrease.

*** Chalk, talc, quartz powder, kaolin, barite or titanium dioxide may be used as fillers. Note that hardness and elongation may change depending on the filler used. For the standard formulations shown here a mixture of talc AT1 and quartz powder W 8 was used. Talc, barite and kaolin are recommended for producing coatings with high chemical resistance.


The elongation of the resulting polymer increases rapidly at a EPS70 / EPS80 content between 55 and 80%. Shore D hardness declines almost linearly in the same interval.

Adhesion testing

Adhesion on concrete surfaces was tested according to DIN.ISO 4624 and DIN EN 1348 using an adhesion testing device (HZP12D1). The result was cohesive breakage of concrete in all cases (**picture 1**)

Crack bridging

Values for crack bridging have been determined according to DIN 28052-6. The widening of crack occurred at a speed of 0.02 mm/min. For all three formulations crack bridging of at least 0.3 mm could be demonstrated (21°C, 1 mm layer). At 0°C crack bridging is 0.2 mm for the green and 0.3 mm for the yellow and the blue formulation. At -20°C we measured 0.2 mm for all samples. With thicker layers and different layer architecture higher values for crack bridging may be reached.

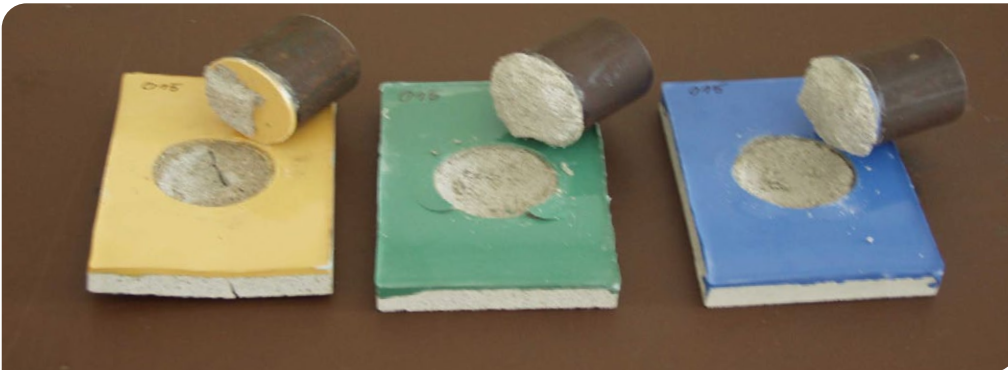

Picture 1: Adhesion on concrete surfaces

Standard formulations using Thioplast® EPS35 polysulfide

Table 11 shows standard formulations with EPS35. The flexibility of the cured EPS35-based material is higher at lower concentrations compared to the aromatic Thioplast® EPS70/80 polysulfides, the aliphatic Thioplast® EPS35 polysulfides are flexibilizing the epoxy formulation way more efficiently .

Table 11: Standard formulations for EPS35

	Formulation 4 EPS35	Formulation 5 EPS35	Formulation 6 EPS35	Formulation 7 EPS35
Component A				
Thioplast® EPS35 polysulfides	10	20	30	40
Bisphenol A resin	65	55	45	35
Filler	20	20	20	20
Pigment	5	5	5	5
Total Component A	100	100	100	100
Component B				
Aradur 2964	31.4	26.7	23.3	20.6
Potting time @ 25°C [h]	>2	>2	>3	>3
Max. elongation [%]	27	50	59	66
Shore D after 21d @ r.t.	74	58	32	20
Strength @ break [N/mm ²]	27	16	9	6

Applicability of EPS Formulations 1 - 7

Formulations 1, 4 and 5

This formulation is only slightly flexibilized. It is recommended for floor coating in facilities with heavy traffic (trucks and fork-lift trucks - meet the German LAU regulations).

Formulations 2 and 6

A low content of EPS70 yields a formulation with low elasticity which is particularly suited for coatings that need to have crack bridging capability. It can be used for storage and handling areas (LAU) for substances that are water hazardous and in sewage plants involving light traffic.

Since this formulation provides excellent barrier properties to water vapor it may be used as a coating material for steel, titanium and PP parts (pipe coating). It is also well suited for heavy duty coatings to be used in industrial areas like slaughterhouses, large-scale catering facilities and laundries where frequent use of hot vapor and aggressive cleaners can be expected.

Formulation 3 and 7

Due to the high content of Thioplast® EPS polysulfides this formulation is highly elastic and is, therefore, particularly suited for the coating of containment basins in tank farms for fuels and chemicals, especially when high tolerance of large temperature differences and extensive motion is expected.

References

This choice of reference projects shall illustrate the versatility of Thioplast® EPS polysulfides in different applications.

Coating of shop floors

Coating of the floor in a wholesale slaughterhouse with Thioplast® EPS polysulfides was applied when conventional EP based coatings failed due to the extreme technical demands. This floor is subjected to wheel traffic and is cleaned frequently with steam cleaning devices and aggressive cleaners. This application requires very good adhesion and tightness, especially at the interface to build-in tables, supports and rails (**picture 2**).



Picture 2: Thioplast® EPS polysulfide coating of the floor in a slaughterhouse

Containment basin for oil and chemicals

The restoration of containment basins for oil tanks requires crack-bridging, chemically resistant coatings, which in addition are insensitive against humidity diffusing from the underground. This coating can be completed by using polysulfide based joint sealants (**picture 3**).

Extreme conditions can be found in truck-wash stations and in chemical plants. The floor coating has to withstand organic solvents, diluted alkali and acids and changes in temperatures. It also needs to have anti-slip properties and to tolerate the mechanical stress caused by traffic of heavy trucks (**picture 4**).



Picture 3: Polysulfide based joint sealant as a crack-bridging, chemically resistant coating



Picture 4: Floor coating of a truck-wash station in a chemical plant

Heavy duty corrosion protection

Good gas tightness, very good resistance to marine climate and excellent adhesion to steel make EPS products ideal candidates for heavy-duty corrosion protection. One example may be the restoration of industrial shipping areas and naval ports (**picture 5**).

Coatings for sewage plants and sewer

The combination of anti-fouling properties, high chemical resistance and low gas diffusion rates suggest the use of Thioplast® EPS polysulfides for coatings of sewage plants and sewers (**picture 6**).

Marine protective coatings

Thioplast® EPS polysulfides are used as components for marine and protective coatings applications.

The material fulfils many specific demands of these applications due to the outstanding properties of Thioplast® EPS polysulfides, e.g. very good adhesion on different surfaces, anti-fouling (formulation dependent) properties and high chemical resistance (**picture 7**).



Picture 5: Heavy-duty corrosion protection of industrial shipping



Picture 6: Thioplast® EPS polysulfide coatings of sewage plant



Picture 7: Marine and protective coatings applications

To find out more about our polysulfides,
visit our website:
nouryon.com/products/thioplast-polysulfides

or contact us at:
E: thioplast@nouryon.com

© Nouryon. All rights reserved.

The information contained in this leaflet is not intended to be exhaustive and is presented in good faith and believed to be correct as of the date on which it is prepared. Persons using the information must make their own determinations and assessments as to the suitability of the relevant information for their purposes prior to taking any action based on the information. Neither Nouryon nor any of its affiliates or representatives makes any representation or warranty, expressed or implied, as to the accuracy or completeness of this document or any of the information contained herein. Nouryon and its affiliates or representatives expressly disclaim to the fullest extent permitted by law any and all liability based, in whole or in part, on the document or any information contained herein.

Thioplast® polysulfides is a trademark of Nouryon in a number of territories worldwide.

Nouryon

Nouryon is a global, specialty chemicals leader. Markets and consumers worldwide rely on our essential solutions to manufacture everyday products, such as personal care, cleaning goods, paints and coatings, agriculture and food, pharmaceuticals, and building products. Furthermore, the dedication of more than 9,700 employees with a shared commitment to our customers, business growth, safety, sustainability and innovation has resulted in a consistently strong financial performance. We operate in over 80 countries around the world with a portfolio of industry-leading brands. Visit our website and follow us @Nouryon and on LinkedIn.

nouryon.com